

Proc. Eurosensors XXV, September 4-7, 2011, Athens, Greece

Fabrication and electromechanical performance of a novel high modulus ionogel micro-actuator

Gokhan Hatipoglu^a, Yang Liu^a, Dean Tigelaar^b, Mitra Yoonessi^b,
Qiming Zhang^a, Srinivas Tadigadapa^{a*}

^a*Department of Electrical Engineering, The Pennsylvania State University, University Park, PA 16802 USA*

^b*NASA Glenn Research Center, Cleveland, OH 44135 USA*

Abstract

In this work, a novel, high modulus sulfonated polymer is utilized as an ionomer for ionic liquid containing micro-ionic actuators (ionogel) is presented. The ionic polymer is composed of one-to-one ratio 4,6-bis(4-hydroxyphenyl)-N,N-diphenyl-1,3,5-triazin-2-amine and 4,4'-biphenol with bis(4-fluorophenyl) sulfone (DPA-PS:BP). The ionogel maintains a relatively higher modulus (700 MPa for 120 wt% of ionic liquid) compared to other widely used ionomers. High modulus of ionogel enables to realize thin films through solution casting. As an initial demonstration of a micro-ionic actuator, an ionic micro cantilever (200 μm x 33 μm x 5 μm) has been micromachined by using focused ion beam (FIB) milling on the substrate. The micro cantilever performance under DC actuation is tested using optical profilometer and a maximum tip displacement is 42 μm at 1.6V was obtained.

© 2011 Published by Elsevier Ltd.

Keywords: Ionic electroactive polymers; ionic liquids; ionomer; micro ionic actuators, ionogel, DPA-PS:BP

1. Introduction

Electroactive polymers (EAPs) are smart materials, which exhibit large mechanical strain (displacements) in response to electrical stimulation. Ionic electroactive polymers (i-EAPs) are a subclass of EAPs where the bending actuation is achieved through the movement of cation and anion pairs inside the polymer matrix as a result of electrical stimulation. The cation-anion pairs are introduced into the polymer matrix through ionic liquids (ILs). ILs are molten organic salts. Due to their high ionic conductivity and large electrochemical potential window (up to 5.7 V between platinum electrodes) [1],

*Srinivas Tadigadapa. Tel.: +1-814-865-2730; Fax: +1-814-865-7065

E-mail address: sat10@psu.edu

Report Documentation Page				Form Approved OMB No. 0704-0188	
Public reporting burden for the collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to a penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.					
1. REPORT DATE SEP 2011		2. REPORT TYPE		3. DATES COVERED 00-00-2011 to 00-00-2011	
4. TITLE AND SUBTITLE Fabrication And Electromechanical Performance Of A Novel High Modulus Lonogel Micro-Actuator				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S)				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) The Pennsylvania State University,Department of Electrical Engineering,University Park,PA,16802				8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)				10. SPONSOR/MONITOR'S ACRONYM(S)	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S)	
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution unlimited					
13. SUPPLEMENTARY NOTES Procedia Engineering 25 (2011) 1337-1340,Government or Federal Purpose Rights License.					
14. ABSTRACT					
15. SUBJECT TERMS					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT Same as Report (SAR)	18. NUMBER OF PAGES 5	19a. NAME OF RESPONSIBLE PERSON
a. REPORT unclassified	b. ABSTRACT unclassified	c. THIS PAGE unclassified			

ILs are widely used in applications such as lithium batteries [2], dye synthesized solar cells [3], actuators [4] and electric double layer capacitors [5]. Melting point of ILs may range from -96°C to 800°C [6]. Most research fields emphasized above require room temperature operation. Therefore, room temperature ionic liquids (RTILs) are generally desired. For this research, 1-methyl-3-butylimidazolium tetrafluoroborate ([BMIm][BF₄]), an imidazolium based RTIL, has been utilized.

ILs act as electrolytes within the ionomer membranes and enhance the electrochemical response of the actuators. For example, the ionic conductivity is increased within the ionomer membrane, which may improve the bending strain and response time [7]. The polymer matrix endows the IL with dimensional and mechanical stability while preserving the electrical conductivity of the IL and any loss of the material due to the outflow of IL. These kind of hybrid materials where ILs are confined within an ionomer membrane are defined as ionogels [8]. Ionogels can be configured as soft sensors and actuators, which are promising for applications such as artificial muscles [9], soft robotics [10], and energy harvesting [11]. They require low voltages, typically 1-5 V, which is limited by the electrochemical potential window of the IL and electrode type. The ionogel actuator configuration is achieved via placing ionogel between two electrode layers. In this work, 50 nm gold layers are embossed on top and bottom surfaces of the ionogel membranes to act as electrodes.

When an electric field is applied through the electrodes, cations drift and diffuse towards cathode, whereas anions drift and diffuse towards anode. For RTIL, there is generally a molecular volume difference between the cation and anion. For [BMIm][BF₄], the BMIm⁺ molecular volume is larger than BF₄⁻. The accumulation of cation and anions at cathode and anode respectively causes a net volume difference, which in turn causes bending of the ionogel. Figure 1(a) schematically illustrates the bending mechanism in ionogels.

Despite the fact that ILs enhance the actuator performance acting as electrolytes within the ionomer, endowing high amounts of IL within the membrane dramatically decreases the elastic modulus of the films. Using solution casting methods, it is very challenging to realize sufficiently thin films out of these ionogels that can be used for the development of microelectromechanical systems (MEMS) scale sensors and actuators. NafionTM is one of the most widely used ionomer in literature that is manufactured by DuPont. For NafionTM, the elastic modulus versus IL uptake has been investigated experimentally and theoretically by Davidson [12]. The theoretical relation between elastic modulus and IL uptake can be mathematically expressed with $E = a_1/w + a_2$ relation, where E is the elastic modulus in MPa, w is the ionic liquid uptake in weight percent and a_1 , a_2 are coefficients for slope and intercept respectively. For example, the elastic modulus of NafionTM is around 40 MPa for 60 weight % of uptake.

In this work, we have developed a novel ionomer [13], which is composed of one-to-one ratio 4,6-bis(4-hydroxyphenyl)-N,N-diphenyl-1,3,5-triazin-2-amine and 4,4'-biphenol with bis(4-fluorophenyl) sulfone (DPA-PS:BP). The elastic modulus of DPA-PS:BP:[BMIm][BF₄] ionogel is measured as 700 MPa for 120 weight % of endowed [BMIm][BF₄]. When compared to NafionTM, this ionomer can form robust thin films due to its higher elastic modulus with endowed ionic liquid. Thin films of 5–7 μm have been realized via solution casting DPA-PS:BP with [BMIm][BF₄]. The chemical structure of DPA-PS:BP is shown in Fig. 1(b).

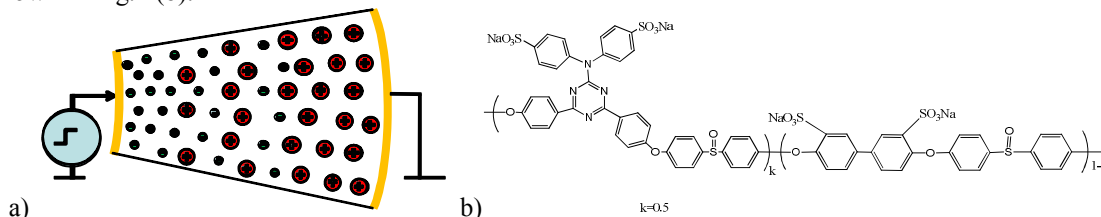


Figure 1: (a) The bending due to molecular volume difference between anion and cation, which accumulate at anode and cathode side. [7] (b) The chemical structure of DPA-PS:BP [13]

Another challenge related to i-EAPs is fabricating micro-structures using these hybrid materials. Most of the traditional MEMS manufacturing techniques such as lithography and wet etching are not applicable with ionogels since the endowed IL within the ionomer tends to outflow when dipped into another solution. To overcome this manufacturability issue, focused ion beam (FIB) milling, was used to fabricate a $200\text{ }\mu\text{m} \times 33\text{ }\mu\text{m}$ cantilever on $5\text{ }\mu\text{m}$ thick DPA PS:BP containing 150 wt % [BMIm][BF₄]. The FIB milling is discussed in the next section. This work demonstrates a free standing cantilever utilizing IL containing i-EAP as a microactuator and should be viewed as an initial work towards more widespread application i-EAPs as new materials for polymer based MEMS.

2. Manufacturing of micro-ionic cantilever via Focused Ion Beam milling

FIB milling is a top-down fabrication method, where finely focused, high energy (momentum) Gallium ions (Ga^+) strike on substrate surface and mill out the material in the region of impact. For milling, FEI Quanta 200 3D FEG Dual Beam Electron Microscope has been used. This model gives the ability to observe the cutting during milling since it has dual beam. For [BMIm][BF₄] containing DPA-PS:BP, the critical parameters are redeposition and cutting time. Redeposition is the deposition of the removed material on the milled region as shown in Fig. 2(a). The redeposition depends on dwell time ($0.1\text{ }\mu\text{s} - 4.8\text{ ms}$) and the ion beam current ($3 - 20\text{ nA}$). These two parameters have to be finely tuned in order to obtain a cleanly cut cantilever while keeping reasonable cutting time and cost. If these parameters are slightly changed, a redeposition run (cutting time: 15 mins, dwell time: $2.4\text{ }\mu\text{s}$, ion current: 20 nA) or a damaged run (cutting time: 20 mins, dwell time: $4.8\text{ }\mu\text{s}$, ion current: 20 nA) are observed as shown in Fig. 2 (a) and (b) respectively. Figure 2(c) shows the cleanly cut cantilever. The overall cutting time is 50 mins with $2.4\text{ }\mu\text{s}$ of dwell time and 7 nA of ion beam current. These are finely tuned parameters for this ionomer-IL combination. The obtained cantilever dimensions are $200 \times 33 \times 5\text{ }\mu\text{m}$. This fabrication method with FIB is also feasible to fabricate arrays and different shaped actuators on the thin film of ionogels.

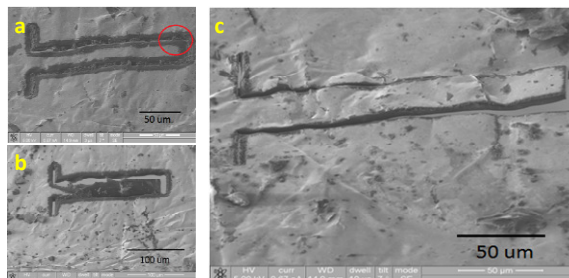


Figure 2:(a) High deposition run (b) High current run, and (c) The cleanly cut and released cantilever.

3. Electromechanical Characterization

After the fabrication of the micro-ionic cantilever, the electromechanical performance is tested. The film with the cantilever pattern on is mounted between two conductive plates. After careful wire bonding, the cantilever is released at the edge of two plates. A potential difference is applied incrementally between the two electrodes of the ionogel. The tip deflection is measured using a white light interferometer (Zygo 100 New View profilometer). Figure 3(a) shows the Zygo image at 1.6 V applied voltage. Figure 3(b) shows the deflection of the cantilever along its length for 3 actuation voltages. The solid lines are smooth fit to the deflection data obtained. Unlike high modulus materials, ionogels are very soft and upon release are very difficult to obtain as cantilevers with smooth surface. This explains some of the observed discrepancy between the smooth fits and the measured data. The maximum tip deflection is measured as $42\text{ }\mu\text{m}$ at 1.6 Volts .

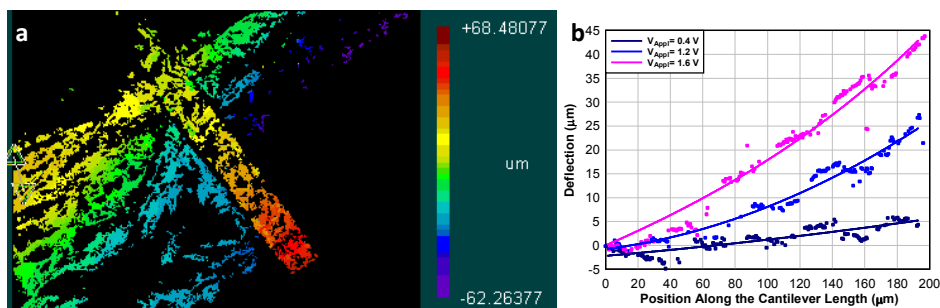


Figure 3.(a) Optical profilometer image of the ionogel cantilever actuated at 1.6 V (b) Deflection profile along the length of the cantilever for 3 different actuation voltages. The experimental data (dots) are fitted to a smooth mathematical function (solid lines) to show the curvature of the cantilever.

4. Conclusion

A high modulus ionomer, DPA-PS:BP, has been investigated as a novel ionomer for IL containing i-EAPs. The higher modulus enables to realize thin film actuators, which can be used for micro sensors and actuators applications. An ionogel microcantilever has been fabricated using FIB etching and is shown as a viable method for micromachining IL containing i-EAPs. Electromechanical characterization of the cantilever showed a maximum tip deflection of 42 μm at 1.6 Volts. The ionomer performance is promising for further investigation.

Acknowledgements

This research is supported by the U.S. Army Research Office under Grant No. W911NF-07-1-0452 Ionic Liquids in Electro-Active Devices (ILEAD) MURI. Gokhan Hatipoglu acknowledges support from Scientific and Technical Research Council of Turkey (TUBITAK) for a 2213-International PhD. Fellowship Programme.

References

- [1] Hapiot, P. and C. Lagrost, *Electrochemical Reactivity in Room-Temperature Ionic Liquids*. Chemical Reviews, 2008. **108**(7): p. 2238-2264.
- [2] Matsumoto, H., H. Sakabe, and K. Tatsumi, *Preparation of room temperature ionic liquids based on aliphatic onium cations and asymmetric amide anions and their electrochemical properties as a lithium battery electrolyte*. Journal of Power Sources, 2005. **146**(1-2): p. 45-50.
- [3] Wang, P., et al., *A New Ionic Liquid Electrolyte Enhances the Conversion Efficiency of Dye-Sensitized Solar Cells*. The Journal of Physical Chemistry B, 2003. **107**(48): p. 13280-13285.
- [4] Lu, W., et al., *Use of Ionic Liquids for π -Conjugated Polymer Electrochemical Devices*. Science, 2002. **297**(5583): p. 983-987.
- [5] Ue, M., et al., *Application of Low-Viscosity Ionic Liquid to the Electrolyte of Double-Layer Capacitors*. Journal of The Electrochemical Society, 2003. **150**(4): p. A499-A502.
- [6] Huddleston, J.G., et al., *Characterization and comparison of hydrophilic and hydrophobic room temperature ionic liquids incorporating the imidazolium cation*. Green Chemistry, 2001. **3**(4): p. 156-164.
- [7] Lin, J., Y. Liu, and Q.M. Zhang, *Charge dynamics and bending actuation in Aquivion membrane swelled with ionic liquids*. Polymer, 2011. **52**(2): p. 540-546.
- [8] Le Bideau, J., L. Viau, and A. Vioux, *Ionogels, ionic liquid based hybrid materials*. Chemical Society Reviews, 2011. **40**(2): p. 907-925.
- [9] Shahinpoor, M. and et al., *Ionic polymer-metal composites (IPMCs) as biomimetic sensors, actuators and artificial muscles - a review*. Smart Materials and Structures, 1998. **7**(6): p. R15.
- [10] Kruusmaa, M., et al. *A linked manipulator with ion-polymer metal composite (IPMC) joints for soft- and micromanipulation*. in *Robotics and Automation, 2008. ICRA 2008. IEEE International Conference on*. 2008.
- [11] Tiwari, R. and K.J. Kim, *Disc-shaped ionic polymer metal composites for use in mechano-electrical applications*. Smart Materials and Structures, 2010. **19**(6): p. 065016.
- [12] Davidson, J.D., *Actuation and Charge Transport Modeling of Ionic Liquid-Ionic Polymer Transducers*, Master of science thesis in Mechanical Engineering. 2010-01-28, Virginia Polytechnic Institute and State University.
- [13] Tigelaar, D.M., et al., *Synthesis and properties of sulfonated and unsulfonated poly(arylene ether triazine)s with pendant diphenylamine groups for fuel cell applications*. Journal of Membrane Science, 2011. **369**(1-2): p. 455-465.